



on is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and reviewing the collection of information, and sending comments regarding this burden estimate or any other aspect of this burdening this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

2. REPORT DATE

July 13, 1994

3. REPORT TYPE AND DATES COVERED

Technical 6/1/93-5/31/94

4. TITLE AND SUBTITLE

Detection of Crosslink Formation by 2 + 2 Photocycloaddition in Poly (Vinyl Cinnamate) by ^{13}C Solid-State NMR

5. FUNDING NUMBERS

G-N00014-91-J-1475
Dr. Kenneth Wynne
R&T Code 4132056

6. AUTHOR(S)

Timothy W. Skloss and James F. Haw

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

Texas A&M University
Chemistry Department
College Station, Texas 77843-3255

8. PERFORMING ORGANIZATION REPORT NUMBER

Technical #7

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)

Office of Naval Research
Chemistry and Physics Division
Ballston Tower 1, Room 503
800 North Quincy Street
Arlington, Virginia 22217-5660

10. SPONSORING/MONITORING AGENCY REPORT NUMBER

11. SUPPLEMENTARY NOTES

Submitted to Macromolecules

12a. DISTRIBUTION/AVAILABILITY STATEMENT

DISTRIBUTION STATEMENT A

Approved for public release
Distribution Unlimited

11/97 94-22584



13. ABSTRACT (Maximum 200 words)

Poly (vinyl cinnamate), PVCN, is one of the more important polymers used in NLO research. It is frequently used as a host polymer into which suitable dyes are introduced, especially those with limited solubilities in other polymers. During the poling process, the polymer may be irradiated with UV light to yield a material with superior SHG retention and reduced solubility. This is frequently assumed to be due to photocrosslinking reactions between cinnamoyl groups in different chains or alternatively between cinnamoyl groups and NLO dye molecules with suitable structures. The mechanism of this crosslinking is proposed to be 2 + 2 cycloaddition of the olefinic groups to yield four-membered-ring crosslink sites. Although this mechanism is appealing in that it is consistent with well characterized reactions in solution, experimental evidence for this important reaction in NLO polymers has been lacking, and its acceptance has not been universal. We demonstrate here that UV irradiation of pure PVCN films results in a partially insoluble material, and that careful comparison of ^{13}C solid state NMR spectra of irradiated films and non irradiated controls reveals that irradiation caused a reduction in olefinic carbon content and an increase in intensity in a region consistent with the proposed crosslink mechanism.

14. SUBJECT TERMS

Poly (vinyl cinnamate) and photocrosslinking

15. NUMBER OF PAGES

8

16. PRICE CODE

17. SECURITY CLASSIFICATION OF REPORT

Unclassification

18. SECURITY CLASSIFICATION OF THIS PAGE

Unclassification

19. SECURITY CLASSIFICATION OF ABSTRACT

Unclassification

20. LIMITATION OF ABSTRACT

UL

NSN 7540-01-280-5500

Standard Form 298 (Rev. 2-89)
Prescribed by ANSI Std. Z39-18
298-102

94 7 19 082 DTIC QUALITY INSPECTED 1

OFFICE OF NAVAL RESEARCH

Grant or Contract N00014-91-J-1475

R&T Code 4132056

Dr. Kenneth Wynne

Technical Report No. 7

**Detection of Crosslink Formation by 2 + 2 Photocycloaddition in Poly (Vinyl Cinnamate)
by ^{13}C Solid-State NMR**

by

Timothy W. Skloss and James F. Haw

Submitted to

Marcromolecules

**Department of Chemistry
Texas A&M University
College Station, TX 77843**

July 13, 1994

**Reproduction in whole, or in part, is permitted for any purpose of the United States
Government.**

This document is approved for public release and sale: its distribution is unlimited.

Detection of Crosslink Formation by 2 + 2 Photocycloaddition in Poly (Vinyl Cinnamate) by ^{13}C Solid State NMR

Timothy W. Skloss and James F. Haw*

Department of Chemistry, Texas A&M University, College Station, Texas 77843


Polymers for nonlinear optics must be prepared with a macroscopic orientation of chromophores in order to yield second harmonic generation (SHG) for frequency doubling applications. Oriented materials are usually obtained by poling the material above T_g in the presence of an intense electric field, and then quenching the material to prevent randomization of chromophore orientation. In practice, slow motion below T_g leads to loss of SHG properties over time, and this problem has had a pervasive influence on research directions in NLO polymers.

One of the more common strategies to stabilize SHG properties is to crosslink the material prior to removing the poling field. Poly (vinyl cinnamate), PVCN, is one of the more important polymers used in NLO research. It is frequently used as a host polymer into which suitable dyes are introduced, especially those with limited solubilities in other polymers. During the poling process, the polymer may be irradiated with UV light to yield a material with superior SHG retention and reduced solubility.¹⁻³ This is frequently assumed to be due to photo-crosslinking reactions between cinnamoyl groups in different chains or alternatively between cinnamoyl groups and NLO dye molecules with suitable structures. The mechanism of this crosslinking is proposed to be 2 + 2 cycloaddition of the olefinic groups to yield four-membered-ring crosslink sites.⁴ Although this mechanism is appealing in that it is consistent with well characterized reactions in solution, experimental evidence for this important reaction in NLO polymers has been lacking, and its acceptance has not been universal. We demonstrate here that UV irradiation of pure PVCN films results in a partially insoluble material, and that careful comparison of ^{13}C solid state NMR

PVCN was obtained from Aldrich and used without further purification. The polymer films were cast from methylene chloride solutions and air-dried. Nominal thickness of the films was measured by a micrometer and estimated at 20 μm . UV radiation at 254 nm was supplied by a Spectroline XX-15F lamp (Fisher Scientific). Three different films were irradiated for 24, 72, and 144 hours. A fourth film was cast as a control and not irradiated. The entire films, typically weighing 200 mg, were removed from the plates and loaded into a 7.5 mm zirconia rotor for magic angle spinning (MAS). T_g for pure PVCN is 357 K, thus spectra were conveniently obtained at room temperature. ^{13}C solid state NMR spectra were obtained at 50 MHz on a home built 4.7 Tesla instrument. Cross polarization⁵ experiments (contact time 1.5 ms, pulse delay 10 s) exhibited reasonable quantitation and substantially greater sensitivity than single pulse experiments, as expected for a polymer below T_g . 1200 scans provided excellent signal to noise. Assignment of the ^{13}C MAS spectrum of the PVCN control (Figure 1) was based on solution spectra and by observing the expected response to interrupted decoupling. Figure 1 reports the assignments and numbering scheme used in this paper. Most significant are the very well resolved signal due uniquely to the olefinic carbon C7 and the well resolved signal from the olefinic carbon C8.

r
☒
☐
☐
 r
 /
 y Codes
 and/or
 ial

eleven different dimer structures; these can conveniently be divided into products of head-to-tail (1) and head-to-head (2) reactions.⁶

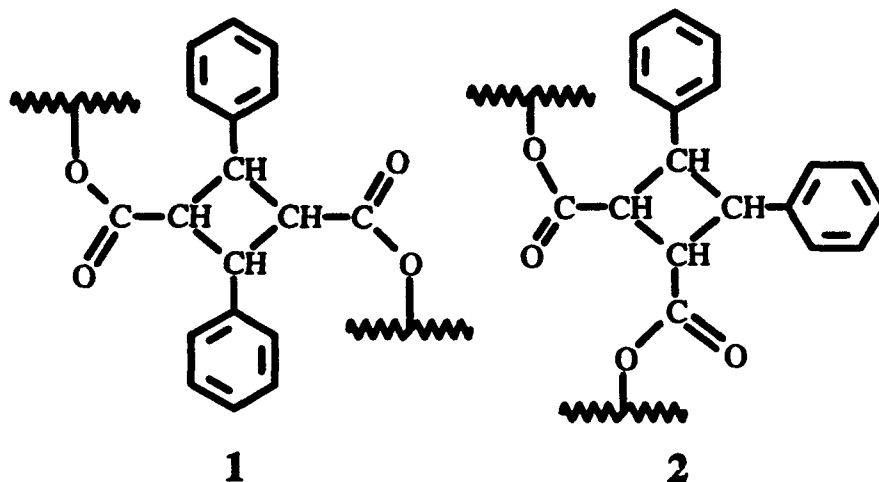

Inspection of Figure 2 shows that the most obvious change upon irradiation is a 15% decrease in the intensities of the olefinic peaks. This intensity was apparently converted into additional signal intensity in the 38-48 ppm region, on top of the resonance for the main chain methylene carbons. We developed a sense of the expected four-membered-ring shifts for structures 1 and 2 by studying reasonable model compounds in spectral data bases and by using the predictive feature of the SPECINFO database on the STN service, which is called SPECAL. We concluded that the aliphatic carbons formed in the proposed crosslinking reaction should have chemical shifts between 38 and 49 ppm, and that the resolution in Figure 2 combined with the complications of stereochemical isomerization would not permit selection between 1 and 2 as the major product. Spectral searching and prediction also indicated that formation of 1 and 2 would be accompanied by a several ppm downfield shift for the carbonyl resonance, and this is very clearly apparent in Figure 2. A smaller predicted change in C1 can also be inferred from the figure. The only apparent anomaly in Figure 2 is that the increase in aliphatic signal intensity is slightly larger than the decrease in olefinic signal intensity, but this observation is easily rationalized

if crosslinking the polymer is assumed to improve cross polarization dynamics. Thus, we conclude that the experimental evidence presented here is strongly supportive of the proposed 2 + 2 photo crosslinking reaction for pure PVCN, but we are unable to determine the detailed stereochemistry of the crosslink site at this time.

Exposing the PVCN films for longer periods of time (72 and 144 hours) did not obviously cause any additional crosslinking. The cycloaddition is a rapid reaction that is usually carried out in a few seconds for the very thin films (2 μm or less) typically prepared for SHG studies. The expected penetration depth of the UV radiation into our polymer film was estimated to be 200 nm or less based on the reported molar absorptivity of ethyl cinnamate in solution and the composition and density of the polymer. Thus, one would expect that less than 1% of the cinnamoyl groups would be photo-crosslinked in our thick films, and this must be reconciled with our observation that extended irradiation converted ca. 15% of the chromophores. We propose that as dimerization occurred on the film surface, the resultant bleaching allowed further penetration of the radiation so that a greater effective penetration depth was realized after protracted irradiation.

This study suggests the ability of solid-state NMR to detect and potentially quantify the extent of photo-crosslinking in a PVCN NLO polymer host-guest system. Future NMR studies will be carried out on insoluble fractions concentrated from photo-crosslinked films as well as efforts to observe reactions with suitable dye molecules. We have previously reported NMR experiments characterizing the time scales of chromophore reorientation,⁷ and investigating the effects of crosslinking on chromophore dynamics would address a central problem in NLO polymer chemistry.


Acknowledgment. This work was supported the Office of Naval Research (Grant No. N00014-91-J-1475).



References

1. Tripathy, S.; Li, L.; Mandal, B. K.; Lee, J. Y.; Kumar, J. *Contemp. Top. Polym. Sci.* **1992**, *7*, 237.
2. Mandal, B. K.; Chen, Y. M.; Lee, J. Y.; Kumar, J.; Tripathy, S. *Appl. Phys. Lett.* **1991**, *58*, 2459.
3. Mandal, B. K.; Kumar, J.; Huang, J. C.; Tripathy, S. *Makromol. Chem., Rapid Commun.* **1991**, *12*, 63.
4. Reiser, A.; Egerton, P. L. *Photogr. Sci. Eng.* **1979**, *23*, 144.
5. Pines, A.; Gibby, M. G.; Waugh, J. S. *J Chem. Phys.* **1973**, *59*, 569.
6. Egerton, P. L.; Hyde, E. M.; Trigg, J.; Payne, A.; Beynon, P.; Mijovic, M. V.; Reiser, A. *J. Am. Chem. Soc* **1981**, *103*, 3859.
7. Taylor, S. A.; Ferguson, D. B.; Haw, J. F. *Macromolecules* **1992**, *25*, 2784.

Figure Captions

1. ^{13}C CP/MAS spectrum of the poly (vinyl cinnamate), PVCN, control film. The assignments and the structure are shown. Asterisks denote spinning sidebands.
2. ^{13}C CP/MAS spectra of a UV-irradiated PVCN film (dashed line) and the non-irradiated control (solid line). The effects of photo-crosslinking, including reduction in olefinic carbon signals and formation of additional intensity in the aliphatic region, are apparent.

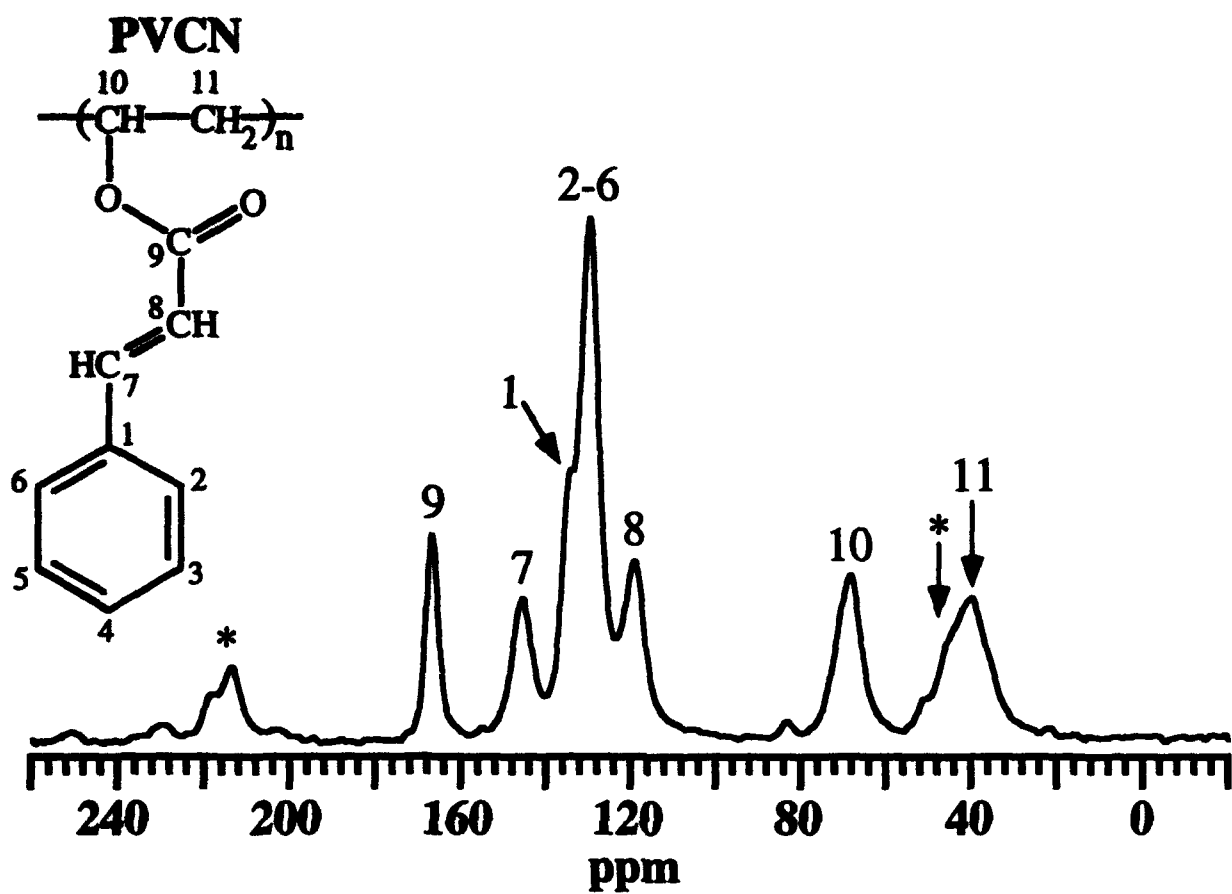

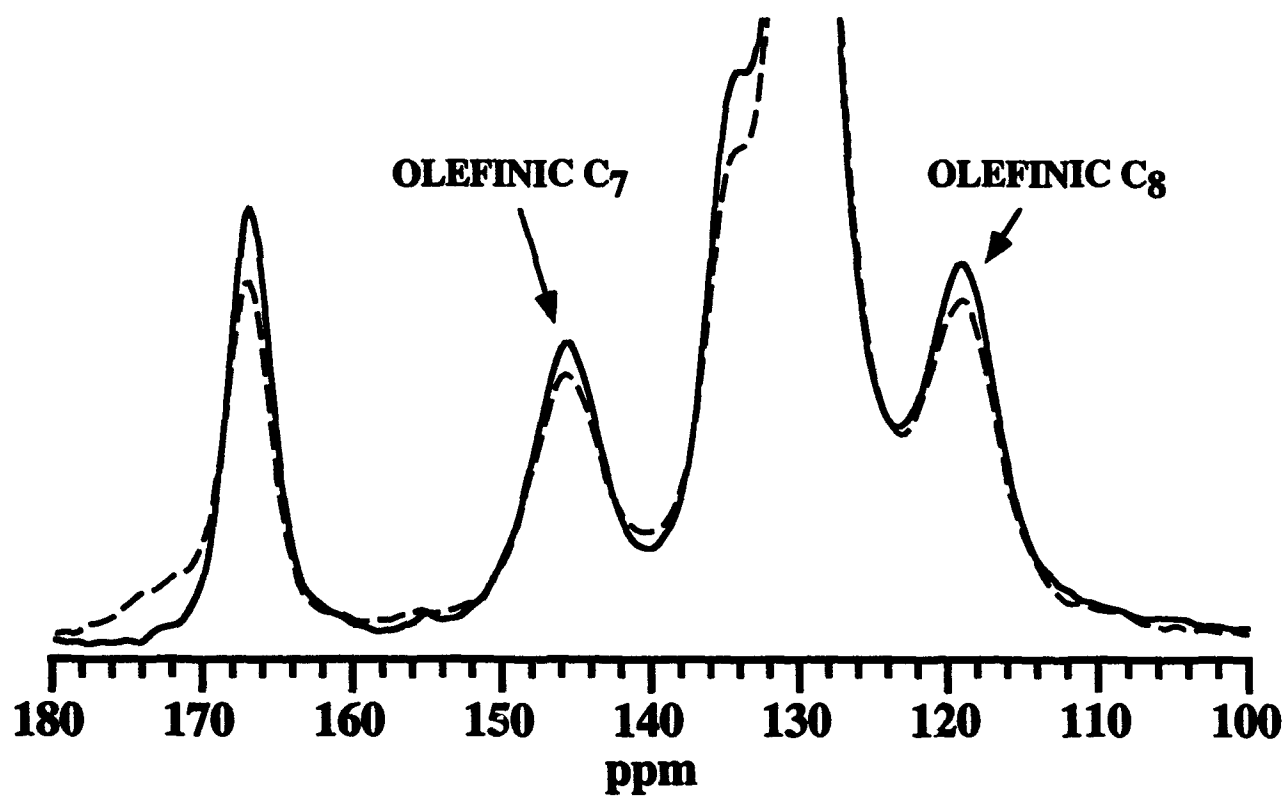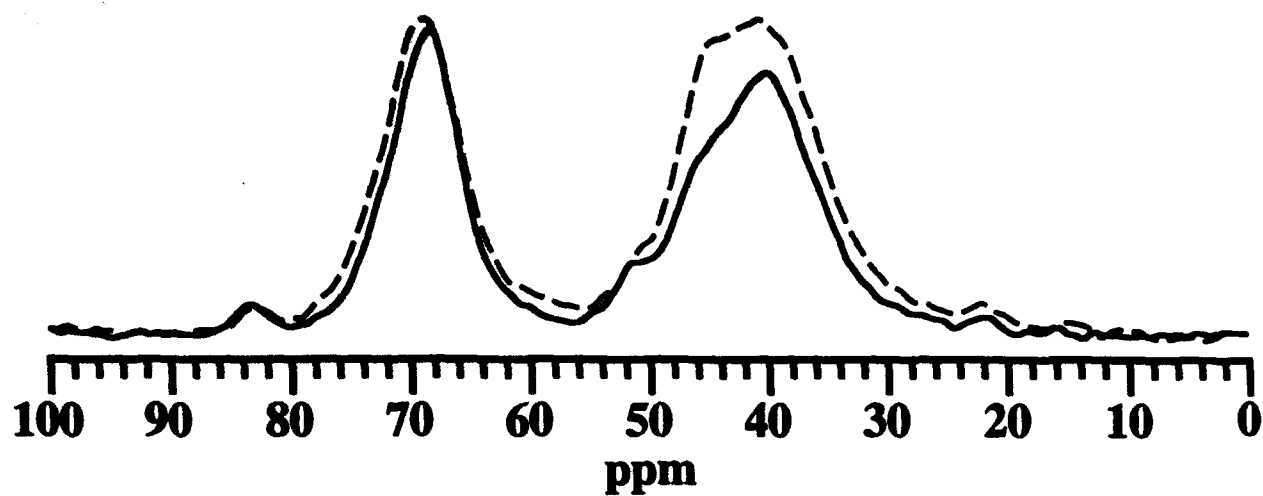

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (1)*
Chemistry and Physics Division
Ballston Tower 1, Room 503
800 North Quincy Street
Arlington, Virginia 22217-5660

Dr. Richard W. Drisko (1)
Naval Civil Engineering
Laboratory
Code L52
Port Hueneme, CA 93043

Defense Technical Information
Center (2)
Building 5, Cameron Station
Alexandria, VA 22314

Dr. Harold H. Singerman (1)
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Eugene C. Fischer (1)
Code 2840
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. Kelvin Higa (1)
Chemistry Division, Code 385
Naval Air Weapons Center
Weapons Division
China Lake, CA 93555-6001

Dr. Bernard E. Douda (1)
Crane Division
Naval Surface Warfare Center
Crane, Indiana 47522-5000

Dr. Peter Seligman (1)
Naval Command, Control and
Ocean Surveillance Center
RDT&E Division
San Diego, CA 92152-5000

* Number of copies to forward